

## Study of an experimental methodology for thermal properties diagnostic of building envelop

Yingying Yang, Alain Sempey, Tingting Vogt Wu, Alain Sommier, Jean Dumoulin, Jean Batsale

### ► To cite this version:

Yingying Yang, Alain Sempey, Tingting Vogt Wu, Alain Sommier, Jean Dumoulin, et al.. Study of an experimental methodology for thermal properties diagnostic of building envelop. EGU 2017 - European Geosciences Union General Assembly, Apr 2017, Vienne, Austria. pp.1, 2017. hal-01651660

**HAL Id: hal-01651660**

**<https://hal.inria.fr/hal-01651660>**

Submitted on 29 Nov 2017

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.


L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



## INTRODUCTION

### Context:

In the energy structure(IEA),buildings represent 35% of total final energy consumption

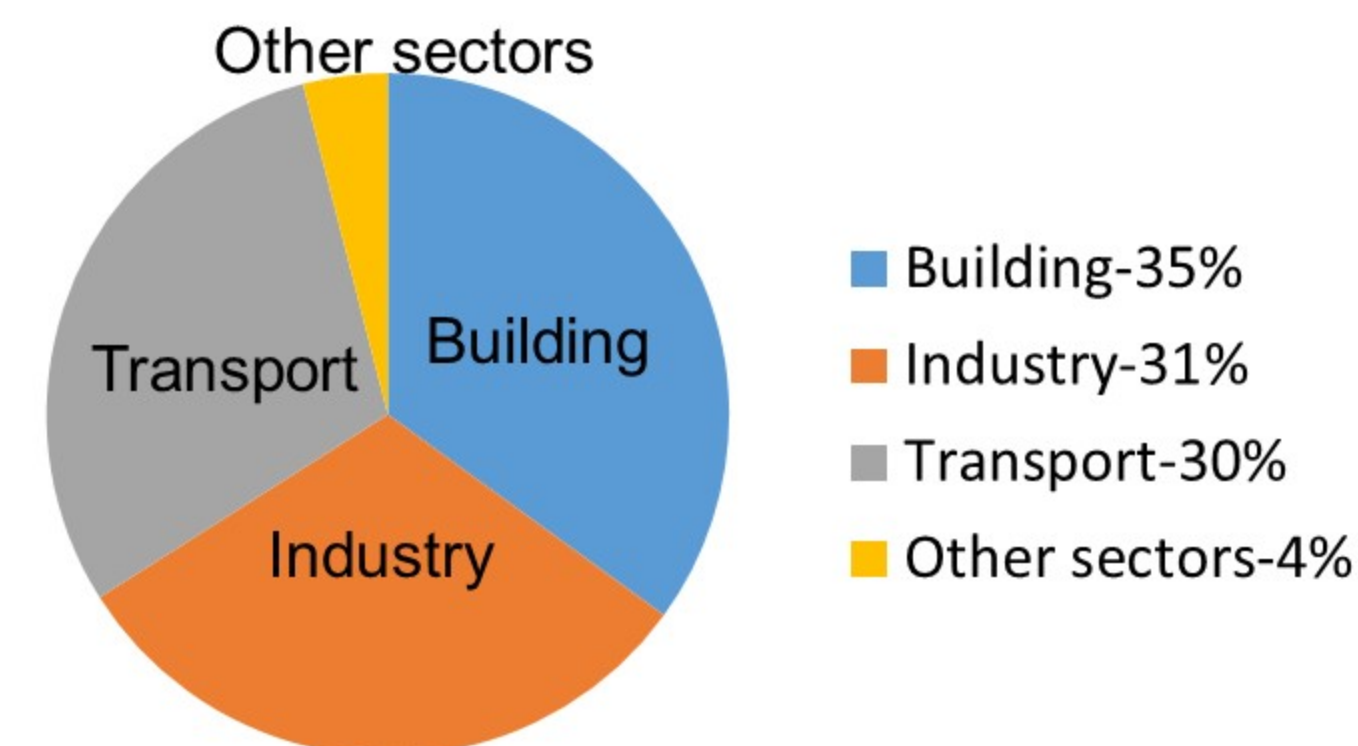

The building envelope plays a critical role in determining levels of comfort and building efficiency. Its real thermal properties characterization is of major interest to be able to diagnose energy efficiency performance of buildings (new construction and retrofitted existing old building).

### Aims:

- Develop new solutions for non-intrusive evaluation of local thermal performance of building walls.
- Investigation of sensors utilization for measuring temperatures and heat flux density of wall, providing some guidelines for the choice of sensors and measurements protocol.
- Applying inverse method to calculate thermal properties based on thermal quadrupoles modelling of wall.

## EXPERIMENTAL SETUP

### Sensors:



Infrared camera FLIR A325



Heat flux meter (Captec)




Peltier module (black and shiny surfaces)

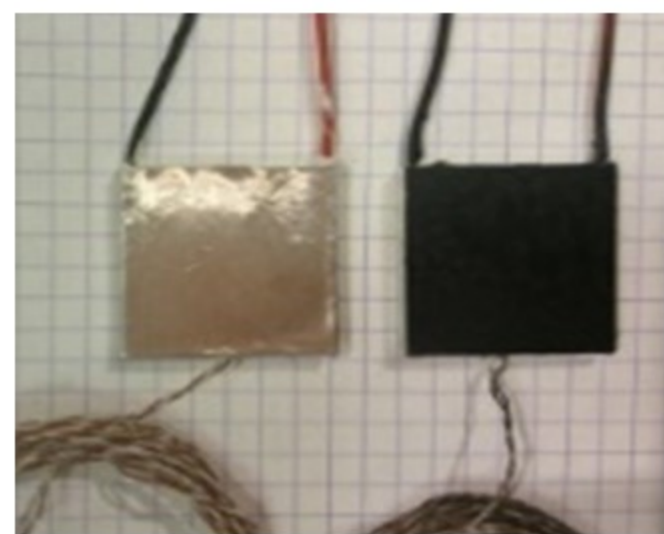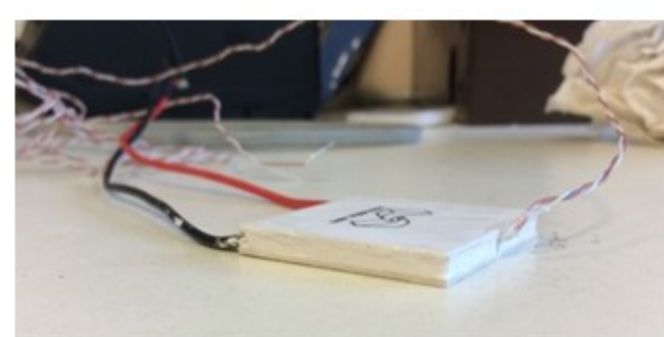

### Objective wall:

A 4-layers wall is tested.

Wall size: height 100 cm; width 70 cm; thickness 25.5 cm

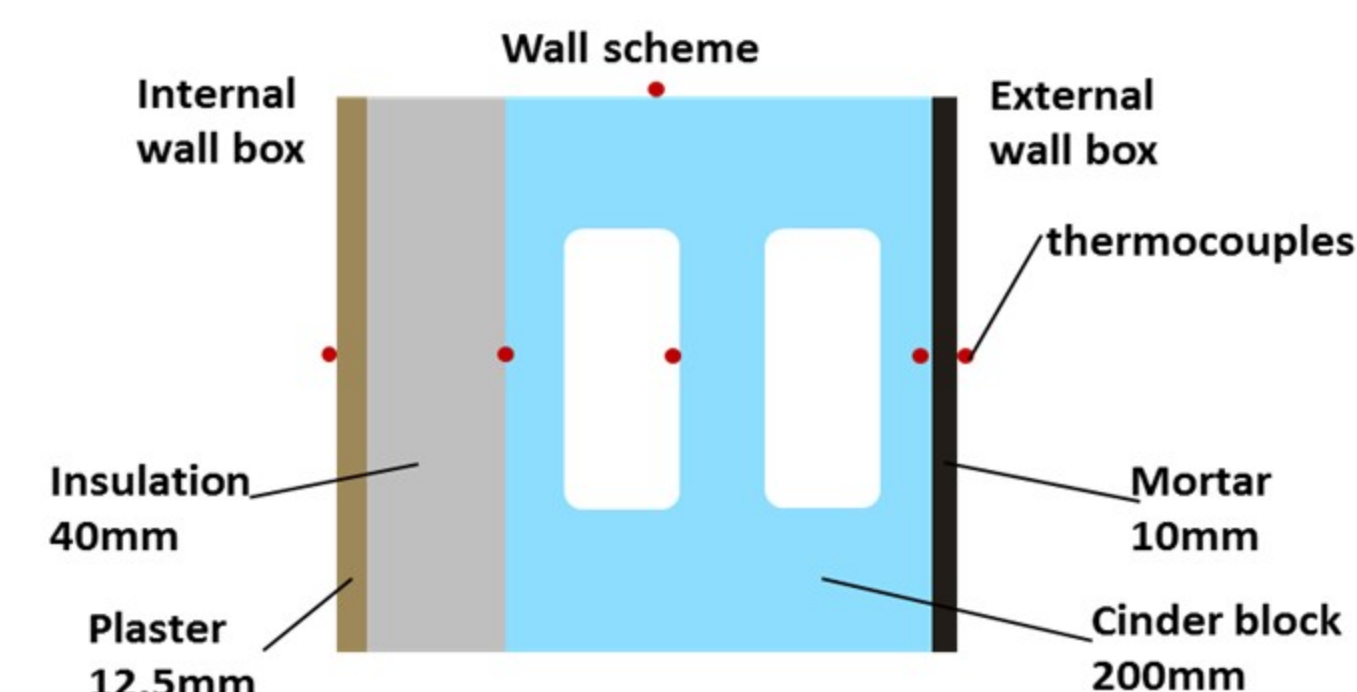

### Experimental system:

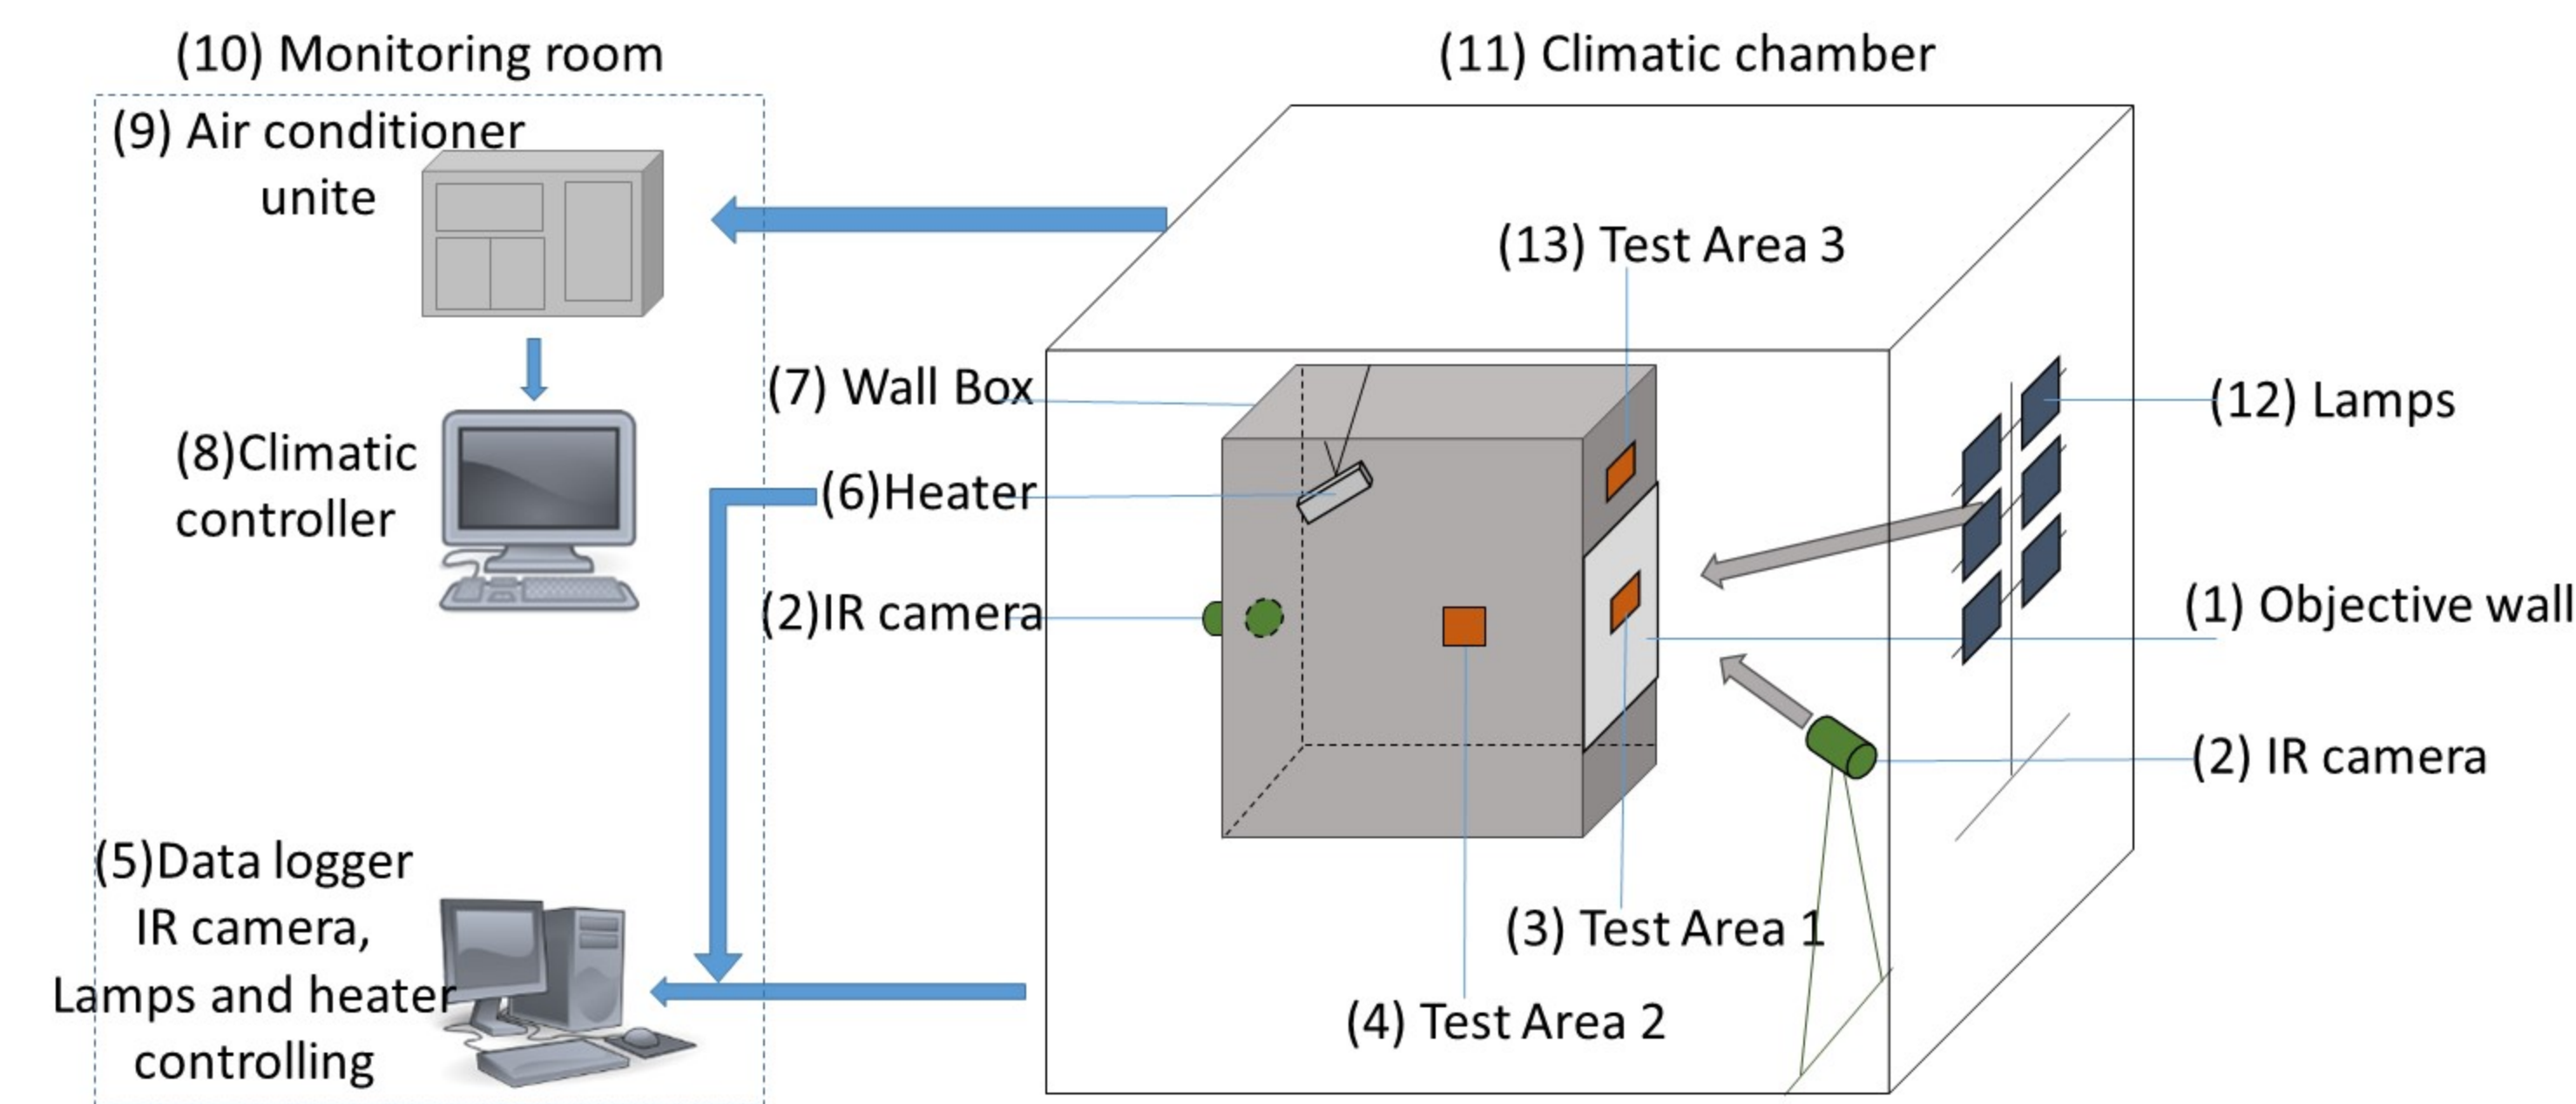


Diagram of experimental apparatus and system

## RESULTS AND ANALYSIS

### Results of emissivity measurement

This emissivity measurement is based on the standard ISO 18434-1:2008(E). The total radiation received by the camera ( $W_{tot}$ ) is  $W_{tot} = W_{obj} + W_{refl} + W_{atm}$ .

If hypothesis that  $\tau_{atm} = 1$ ,  $\epsilon_{crum\_Alu} = 0$ ,  $T_{refe} = T_{obj}$ , the emissivity of target surface can be

computed as:  $\epsilon_{obj} = \epsilon_{refe} \cdot \frac{W_{tot}^{obj} - W_{tot}^{refl}}{W_{tot}^{refe} - W_{tot}^{refl}}$



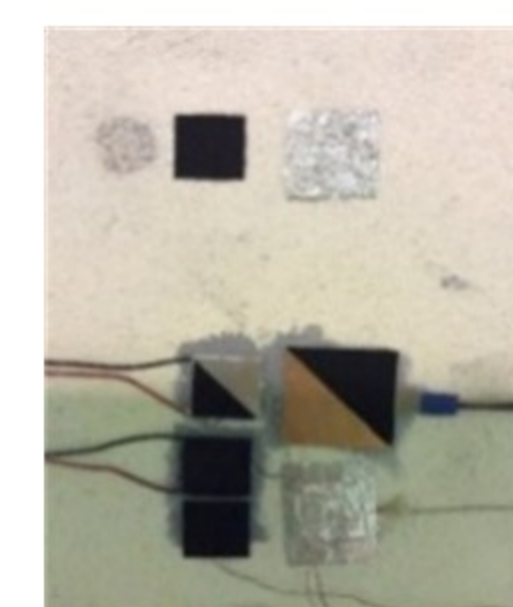


Photo of test area

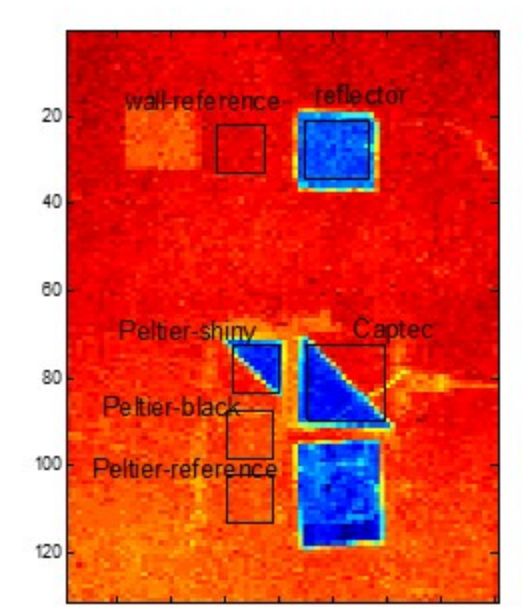

Infrared image of test area

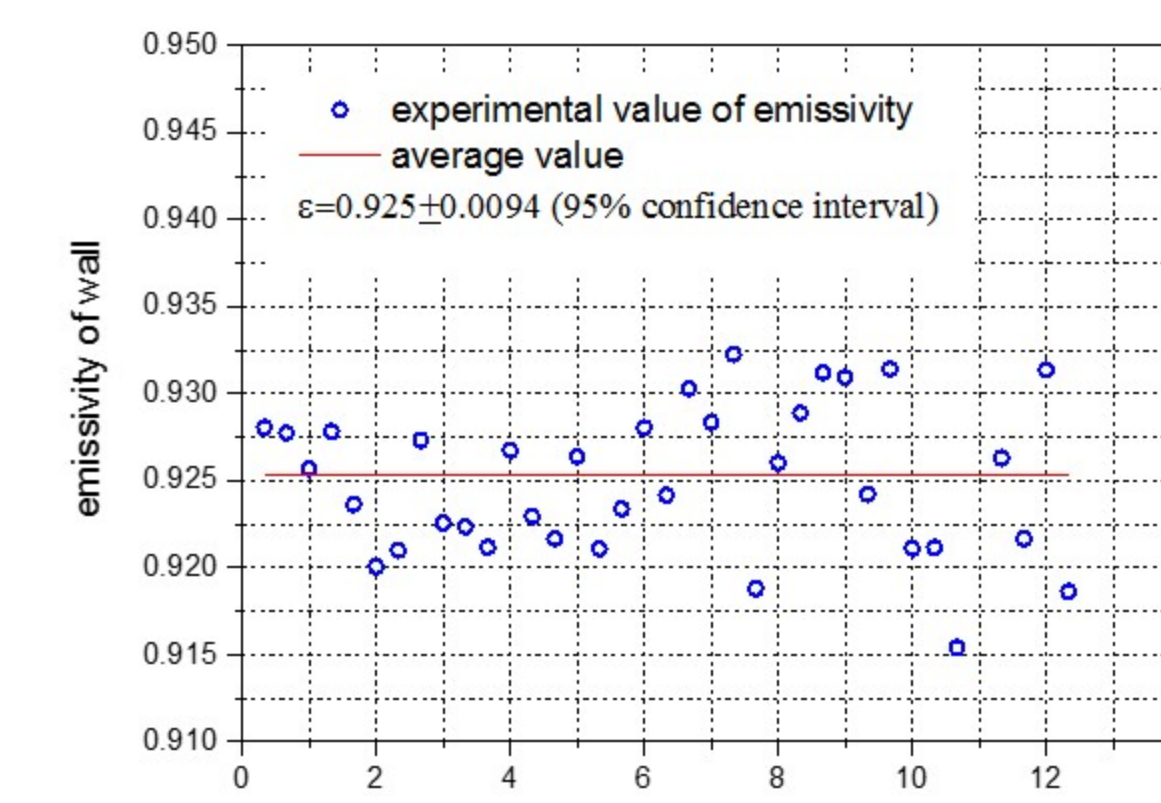

Results of emissivity


### Results of heat flux

The heat flux balance of wall surface is:


$$Q_{tot} = G + Q_{cov} - E - G_{refl};$$

$$Q_{tot} = a G + h(T_{air} - T_{sur}) - \epsilon \cdot \sigma \cdot T_{sur}^4$$


The heat flux of convection, radiation and transmittance for wall are computed out based on heat flux balance.

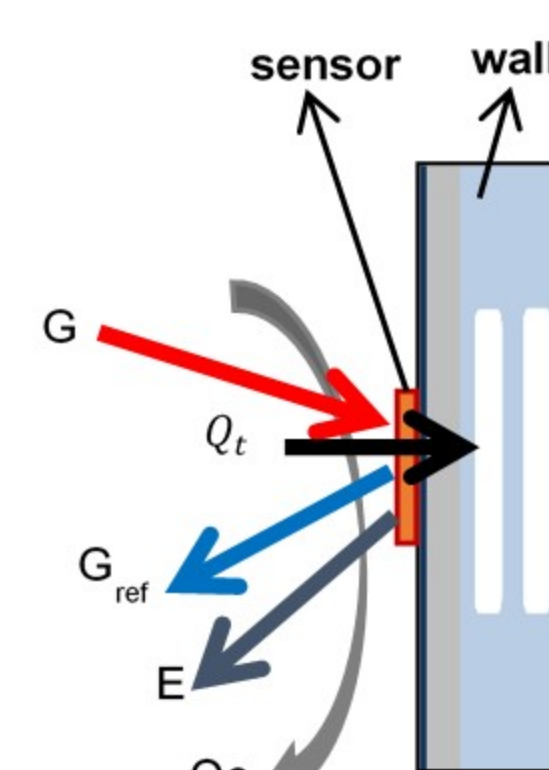

Heat flux balance of surface

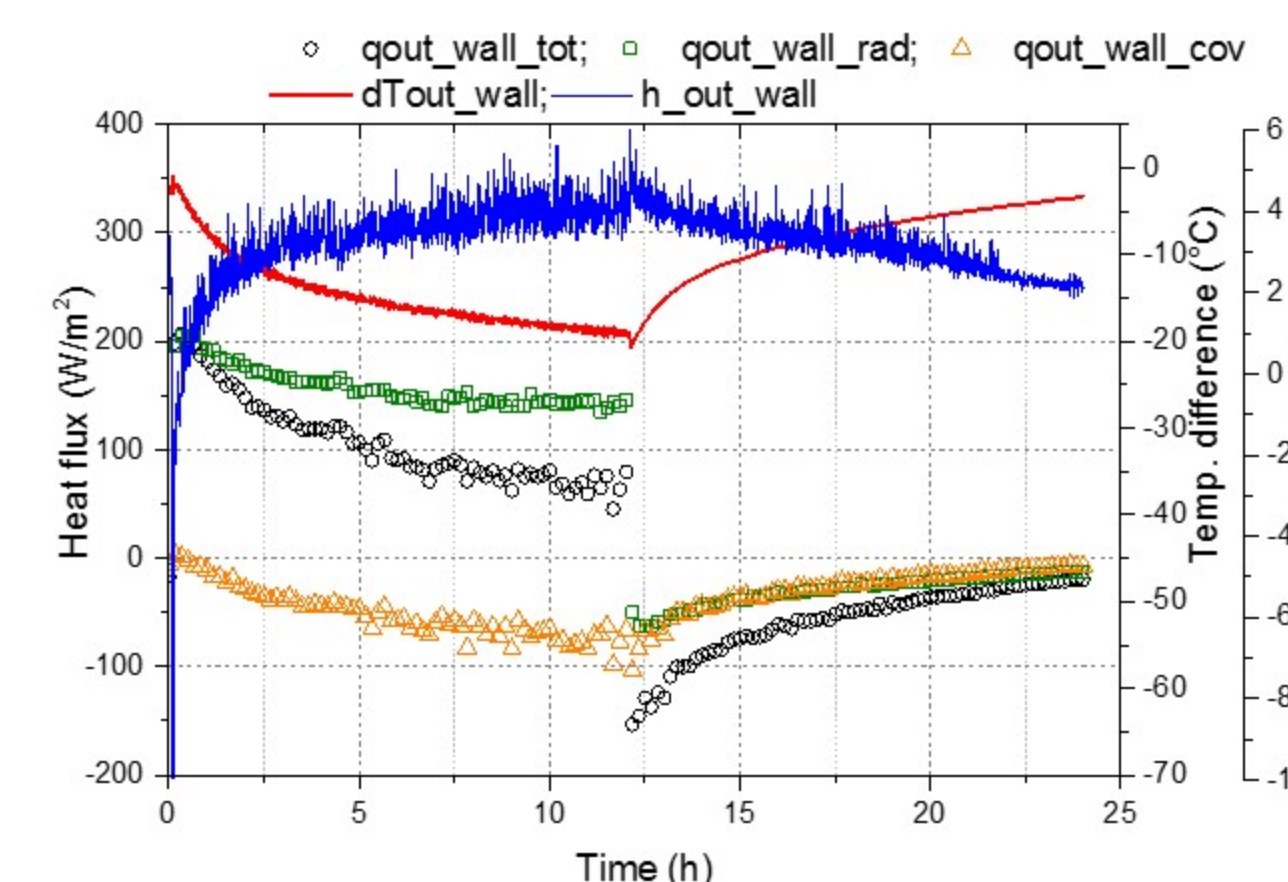


Heat flux of convection, radiation and transmittance of wall

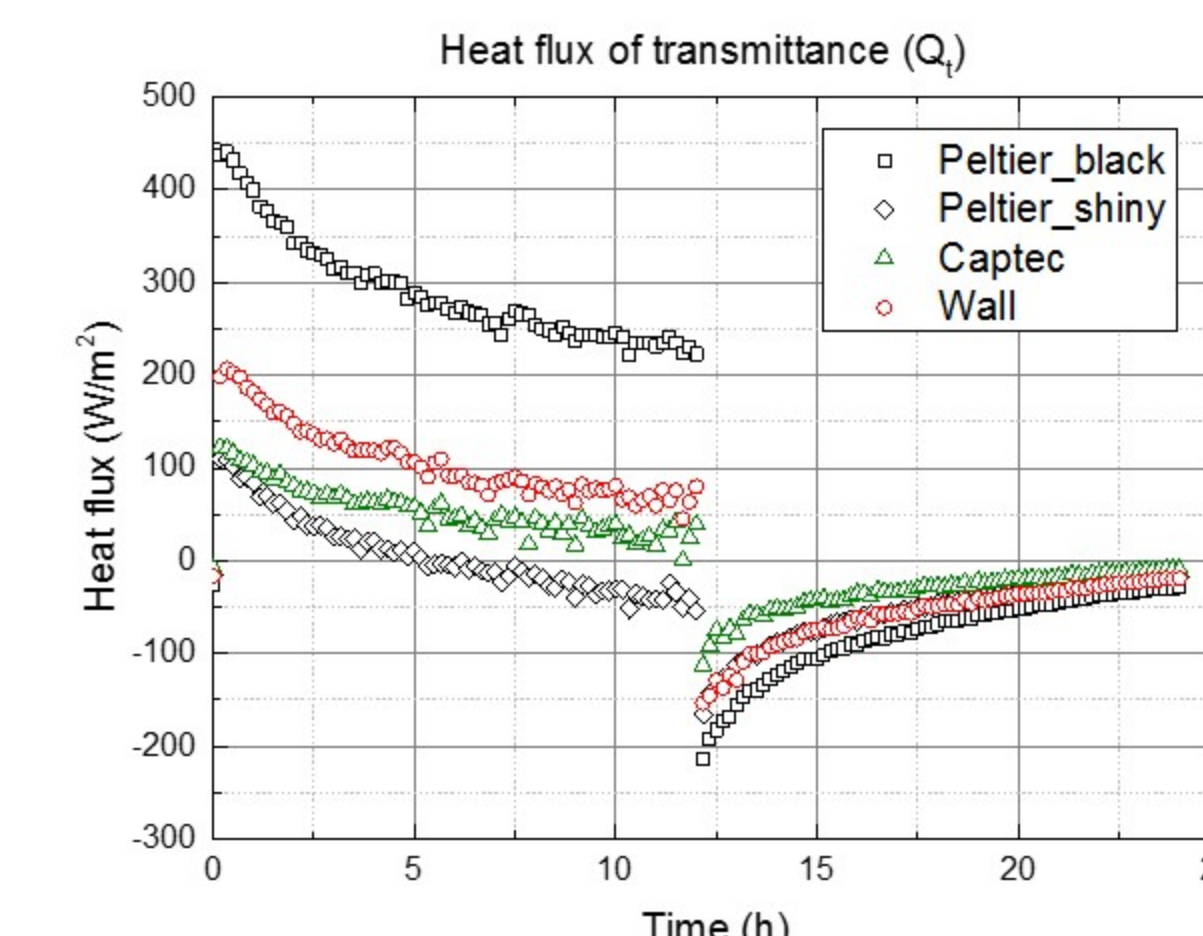


Comparison for heat flux of 4 surfaces ( wall, Captec fluxmeter, shiny Peltier, black Peltier)

### Inverse method

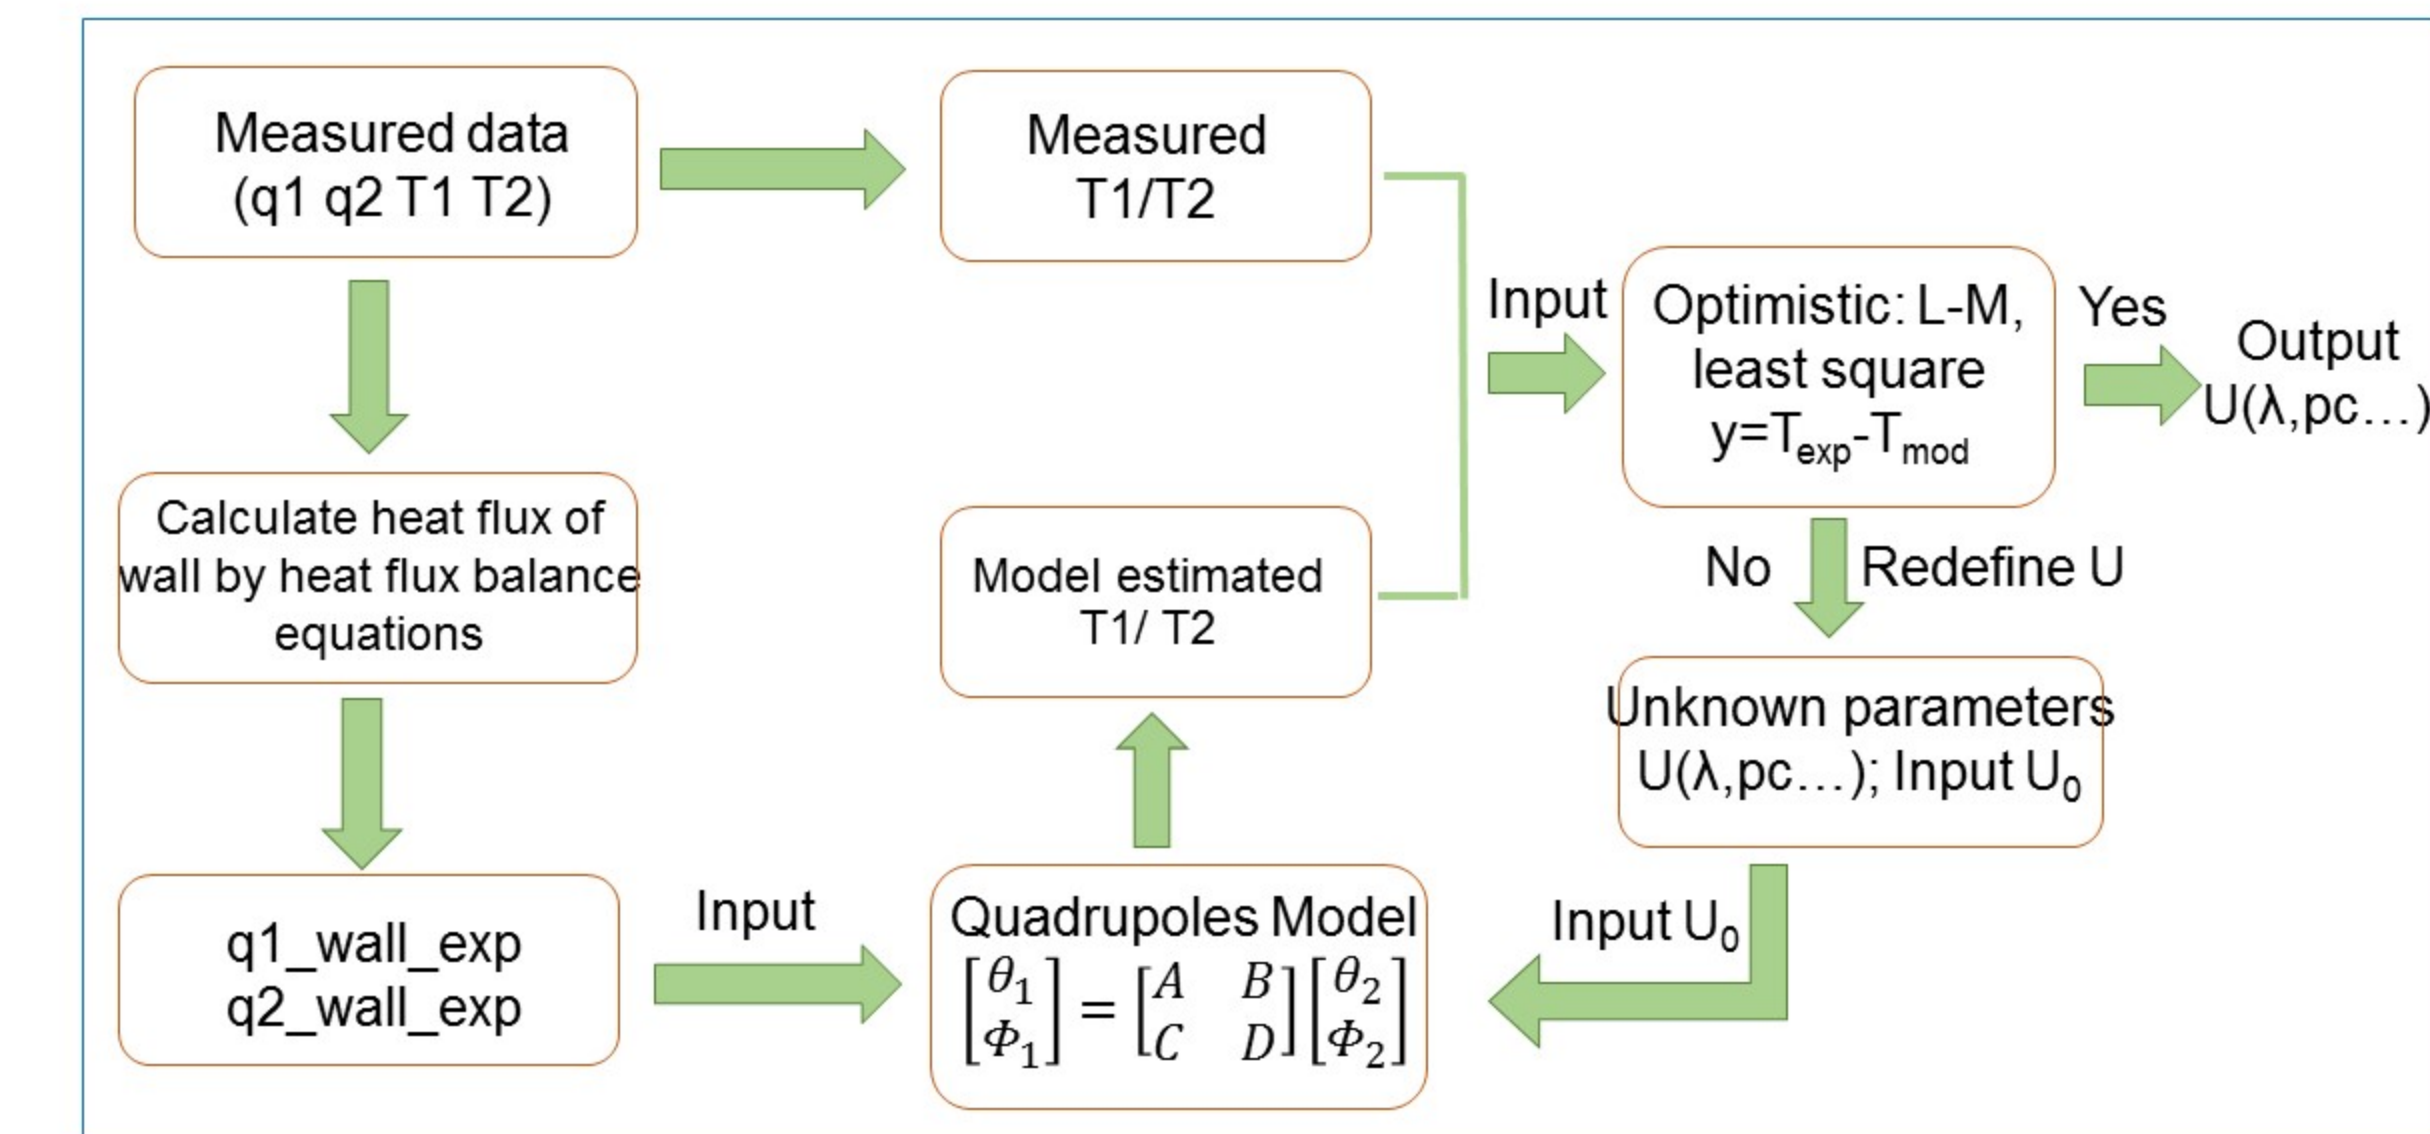

### Sensitivity analysis

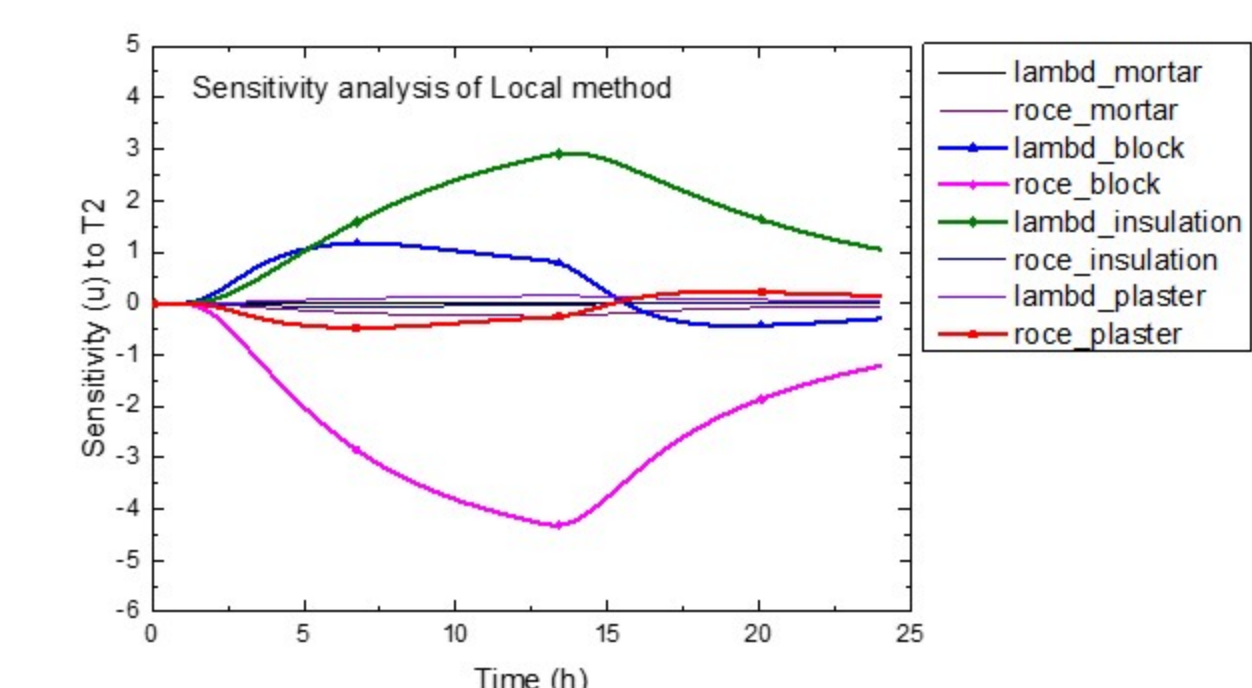

Sensitivity of rear face temperature

For the optimization of front face temperature T1,  $U = (\lambda_{mortar} \rho_{Cmortar} \lambda_{block} \rho_{Cblock})$ . The optimization time is between 1-5 hours.

For the optimization of rear face temperature T2,  $U = (\lambda_{block} \rho_{Cblock} \lambda_{insulation} \rho_{Cplaster})$ . The optimization time is between 5-10 hours.

### Optimization results

Based on the sensitivity analysis, 6 thermal parameters were optimized by inverse method with the measured heat flux and temperature of wall

	$\lambda_{mortar}$ (W/mK)	$\rho_{Cmortar}$ (10 <sup>6</sup> J/m <sup>3</sup> K)	$\lambda_{block}$ (W/mK)	$\rho_{Cblock}$ (10 <sup>6</sup> J/m <sup>3</sup> K)	$\lambda_{insulation}$ (W/mK)	$\rho_{Cplaster}$ (10 <sup>6</sup> J/m <sup>3</sup> K)
Test 1	1.17	2.36	0.84	0.92	0.045	0.53
Test 2	1.70	2.27	0.86	1.02	0.051	0.64
Test 3	1.45	2.45	0.84	0.99	0.056	0.69
Test 4	1.47	2.64	0.80	0.99	0.046	0.69
Advantage values	1.45	2.43	0.83	0.98	0.050	0.64
Reference values	1.15	1.70	0.87	0.90	0.038	0.90

## CONCLUSIONS

- Emissivity of wall is measured with an infrared camera through an improved reduced data process.
- Peltier sensors are applied and analyzed for the measurement of heat flux in this test.
- Heat flux of radiation, convection and transmittance for wall is obtained by heat flux balance equation.
- The thermal properties of wall is characterized by an inverse method based on the thermal quadrupoles modelling.